

Report No.: 68260LC10007901 Page 1 of 16

Test Report

Client Name : SHENZHEN REFOND OPTOELECTRONICS CO .,LTD

Address Bright new district of shen hen tian Lao 10 industrial

one 1

Product Name : SMD3014-C13

Date : 2021-04-06

Compliance Labo

Shenzhen Anbotek Pengcheng Compliance Laboratory Limited

Report No.: 68260LC10007901 Page 2 of 16

Report No.: 68260LC10007901

Product Description: SMD3014-C13

Model No.: RF-27TC13DS-EC-N-Y

Test Initiation Date: 2020-02-07

Test Completion Date: 2021-02-26

Test Standard: IES LM-80-15

Test Laboratory: Shen hen Anbotek Pengcheng Compliance Laboratory Limited

Zone B, 1/F., Building 2, Phase III, Huangtian Yangbei Industrial

Hora Zlang

Testing location: Zone, Huangtian Community, Hangcheng Street, Bao'an District,

Shen hen, Guangdong, China.

Tested by

Reviewed by

Lenin Ye/ Lewin Ye

Flora Zhang/

Note: This test report is prepared for the customer shown above and for the device described herein. It may not be duplicated or use in part without prior written consent from Shen hen Anbotek Pengcheng Compliance Laboratory Limited. This report must not be used by the customer to claim product certification, approval, or endorsement by NVLAP, NIST, or any agency of the Federal Government.

TABLE OF CONTENTS

| 1 General Information | 3 |
|--|---|
| 2 Summary of Test Result | |
| 3 Test Method | |
| 3.1 Photometric and Electrical Measurement | |
| 3.2 Season the LED from 0 hours to 9000 hours | |
| 4 Test Data | |
| 4.1 Data Set 1: 55 C, 60 mA (Lumen Maintenance) | 8 |
| 4.2 Data Set 1: 55 C, 60 mA (Chromaticity Shift) | |
| 4.3 Data Set 2: 85 C, 60 mA (Lumen Maintenance) | |
| 4.4 Data Set 2 | |

Report No.: 68260LC10007901 Page 4 of 16

1 General Information

1.1 Product Description for Device under Test (DUT)

Part Number: SMD3014-C13

Part type: RF-27TC13DS-EC-N-Y

Nominal CCT: 2700K

Nominal CRI: 90

Nominal Input Power(W): 0.18W

Mean Initial Forward Voltage(V): 3V

Nominal LED Die Area(mm²): 0.07mm

Average Current per LED Die(mA): 60mA

Average current density per LED Die(mA/mm²): 830.24mA/mm

Average power per LED Die(W): 0.18W

Average power density per LED Die(W/mm²): 2.49W/mm

Family products covered by this report:

According to ENERGY STAR Requirements for the Use of LM-80 Data, the following products can be covered by this report base on the information and declaration provided by manufacturer. The information of these models shows that the covered products meet all section 4 requirements of ENERGY STAR Requirements for the Use of LM-80 Data (September 28, 2017)

This report covers the following models:

Report No.: 68260LC10007901

| Series Name | Model name | Number of dies | Average current density per LED die (mA/mm 2) | Current mA | power intensit y W/m m2 | Powe r W | distance between of dies (mm) | Seri es | Par allel | Driver current of die |
|-------------|-------------------------|-------------------|---|---------------|-------------------------------------|----------------|--|------------|--------------|-----------------------------|
| SMD3014-C13 | RF-27TC13DS-EC- N-Y | 1 | 830.24 | 60 | 2.49 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-***C13DS-EC- N-Y | 1 | 830.24 | 60 | 2.49 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-****C13DS-EC- F-Y | 1 | 415.12 | 30 | 1.25 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-***C13DS-EC-Y | 1 | 276.75 | 20 | 0.83 | 0.06 | 0 | 0 | 0 | 20 |
| SMD3014-C13 | R*-****C13DS-EE- N-Y | 1 | 830.24 | 60 | 2.49 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-***C13DS-EE- F-Y | 1 | 415.12 | 30 | 1.25 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-***C13DS-EE-Y | 1 | 276.75 | 20 | 0.83 | 0.06 | 0 | 0 | 0 | 20 |
| SMD3014-C13 | R*-****C13DS-BF- N-Y | 1 | 737.59 | 60 | 2.21 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-****C13DS-BF- F-Y | 1 | 368.80 | 30 | 1.11 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-***C13DS-BF-Y | 1 | 245.86 | 20 | 0.74 | 0.06 | 0 | 0 | 0 | 20 |
| SMD3014-C13 | R*-***C13DS-CF- N-Y | 1 | 465.00 | 60 | 1.40 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-****C13DS-CF- F-Y | 1 | 232.50 | 30 | 0.70 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-***C13DS-CF-Y | 1 | 155.00 | 20 | 0.47 | 0.06 | 0 | 0 | 0 | 20 |
| SMD3014-C13 | R*-****C13DS-HH- N-Y | 1 | 410.26 | 60 | 1.23 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-****C13DS-HH- F-Y | 1 | 205.13 | 30 | 0.62 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-****C13DS-HH-Y | 1 | 136.75 | 20 | 0.41 | 0.06 | 0 | 0 | 0 | 20 |
| SMD3014-C13 | R*-****C13DS-DF- N-Y | 1 | 368.51 | 60 | 1.11 | 0.18 | 0 | 0 | 0 | 60 |
| SMD3014-C13 | R*-****C13DS-DF- F-Y | 1 | 184.25 | 30 | 0.55 | 0.09 | 0 | 0 | 0 | 30 |
| SMD3014-C13 | R*-***C13DS-DF-Y | 1 | 122.84 | 20 | 0.37 | 0.06 | 0 | 0 | 0 | 20 |

Page 6 of 16

Report No.: 68260LC10007901

Note:

$$\frac{R^*-*}{A1} - \frac{*}{A2} - \frac{*}{A3} - \frac{*}{A4} - \frac{*}{A5} - \frac{*}{A6} - \frac{*}{A7} - \frac{*}{A8}$$

Identifiers Information (if any):

A1:Letter R* can be RF or RT RG ,It is an internal Market code which does not affect property.

A2:Letter * represent customer name It can be C D H K L M P S T W Y And so on or empty

A3: Letter ** represent CCT It can be 27 30 35 40 45 50 57 60 62 65; ** does not just refer to two numbers, it may also be like the previous mentioned 2, 3, 4, 5, 6, 7, etc.

A4:Letter * represent workshop code, it can be R,M,H,T or Q&S which does not affect product property A5:Letter C13DS is a fixed code

A6:Letter ** represent chip type, it can be EC,HH,BF,CF,DF,EF,FF or FH Code, etc., the models with code EC use the smallest si e chip.

A7:Letter ** represent current, it can be E(20mA), F(30mA) or N(60mA). Code E is a general rule and may be omitted As the voltage of above models is always 3V, Code N represents the max power. A8:A (-Y) means the centrifugal power equipment is not used ,No (-Y) means the equipment is used.

1.2 Standards Used

IESNA LM-80-15: IES Approved Method for Measuring Luminous Flux and Color Maintenance of LED, Arrays and Modules.

ENERGY STAR® Program Guidance Regarding LED Package, LED Array and LED Module Lumen Maintenance Performance Data Supporting Qualification of Lighting Products (This test method was not accredited by NVLAP)

1.3 Test Facility Description

The test facility used by Shen hen Anbotek Pengcheng Compliance Laboratory Limited is located at Zone B, 1/F., Building 2, Phase III, Huangtian Yangbei Industrial Zone, Huangtian Community, Hangcheng Street, Bao'an District, Shen hen, Guangdong, China.

1.4 Test Equipment List

| Device | Manufacture | Model No. | Serial No. | Calibration Date | Calibration Due Date |
|----------------------------|-------------|------------|------------|------------------|-------------------------|
| Digital Power Meter | YOKOGAWA | WT210 | SE-074 | 2020-05-06 | 2021-05-05 |
| LM-80 Aging Test System | KEYI | KY-3X-LH60 | SE-564 | 2020-05-06 | 2021-05-05 |
| DC Power Supply | EVERFINE | WY605 | SE-605 | 2020-05-06 | 2021-05-05 |
| Standard Lamp | OSRAM | 12V/10W | SE-2243 | 2020-09-25 | 2021-09-24 |
| Spectrum Analy er | EVERFINE | HAAS-2000 | SE-607 | 2020-05-06 | 2021-05-05 |
| Integrating Sphere (0.5m) | EVERFINE | AIS-2 | SE-608 | Before use | Before use |

Page 8 of 16

Report No.: 68260LC10007901

2 Summary of Test Result

| Data Set | 1 | 2 | 3 |
|---|--|--|--|
| Nominal case temperatures | 55 C | 85 C | 105 C |
| Drive Current | 60 mA | 60 mA | 60 mA |
| Condition | Ts=54.9 C Ta=54.7 C R.H. 65% IF=60 mA | Ts=84.7 C Ta=84.3 C R.H. 65% IF=60 mA | Ts=104.8 C Ta=103.7 C R.H. 65% IF=60 mA |
| sample si e | 25 | 25 | 25 |
| Duration (in Hours) | 9000 | 9000 | 9000 |
| Intervals (in Hours) | 1000 | 1000 | 1000 |
| Failures Observed | 0 | 0 | 0 |
| Average Lumen Maintenance at 9000h | 97.37% | 96.98% | 96.48% |
| Average Chromaticity Shift at 9000h | 0.0022 | 0.0027 | 0.0034 |
| | 4.417E-06 | 4.473E-06 | 4.510E-06 |
| | 1.013 | 1.010 | 1.005 |
| Reported L ₇₀ (9000h) TM-21 Lifetime | >54000 | >54000 | >54000 |
| Reported L ₈₀ (9000h) TM-21 Lifetime | 53000 | 52000 | 51000 |
| Reported L ₉₀ (9000h) TM-21 Lifetime | 27000 | 26000 | 24000 |





Report No.: 68260LC10007901 Page 9 of 16

3 Test Method

3.1 Photometric and Electrical Measurement

Total light output (luminous flux) for the 25 C 1 C ambient temperature conditions is measured using a integrating sphere. Each LED is operated at rated drive current (DC Mode).

The total uncertainty of the light output measurements is estimated, at the 95% confidence level, not to exceed 1.6% over the wavelength range 380-800nm.

3.2 Season the LED from 0 hours to 9000 hours

Three LM-80 aging measurement system Temperature Chambers are using for Seasoning, and the temperature is set to 55 C, 85 C, 105 C (manufacture defined), the airflow is minimum to keep the uniformity to temperature. LED are operated steady state (no cycling) for a period of 9000 hours, checked the lumen flux and Chromaticity Shift every 1000 hours. The samples are inspected at regular intervals (24 hours) throughout the 9000 hours. The time and date of failure of each lamp is recorded. The actual elapsed time for each light LED is in hour.

Page 10 of 16

Report No.: 68260LC10007901

4 Test Data

4.1 Data Set 1: 55°C, 60 mA (Lumen Maintenance)

Description of Light Sources Tested: RF-27TC13DS-EC-N-Y

Casc ta

4.2 Data Set 1: 55°C, 60 mA (Chromaticity Shift)

| Description of Light Sources Tested: | RF-27TC13DS-EC-N-Y |
|--------------------------------------|--------------------|
| Case Temperature: | 54.9 C |
| Ambient Temperature: | 54.7 C |
| Drive Current: | 60 mA |
| Measure Current: | 60 mA |
| Failures Observed: | None |

| Chrom | aticity | Shift (| u'v') |
|-------|----------|---------|-------|
| | Ialicity | JIIII | u v , |

| Sample No. | u | V | CCT(K) | 1000 hrs | 2000 hrs | 3000 hrs | 4000 hrs | 5000 hrs | 6000 hrs | 7000 hrs | 8000 hrs | 9000 hrs |
|---------------|--------|--------|--------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| L1 | 0.2599 | 0.5347 | 2724 | 0.0004 | 0.0007 | 0.0005 | 0.0010 | 0.0014 | 0.0014 | 0.0017 | 0.0019 | 0.0021 |
| L2 | 0.2569 | 0.5335 | 2792 | 0.0005 | 0.0004 | 0.0004 | 0.0010 | 0.0013 | 0.0011 | 0.0012 | 0.0017 | 0.0020 |
| L3 | 0.2631 | 0.5366 | 2653 | 0.0003 | 0.0003 | 0.0009 | 0.0009 | 0.0012 | 0.0016 | 0.0016 | 0.0020 | 0.0018 |
| L4 | 0.2606 | 0.5353 | 2708 | 0.0005 | 0.0008 | 0.0007 | 0.0012 | 0.0009 | 0.0012 | 0.0019 | 0.0015 | 0.0017 |
| L5 | 0.2594 | 0.5350 | 2733 | 0.0003 | 0.0003 | 0.0010 | 0.0009 | 0.0016 | 0.0017 | 0.0019 | 0.0023 | 0.0022 |
| L6 | 0.2601 | 0.5355 | 2716 | 0.0004 | 0.0005 | 0.0006 | 0.0011 | 0.0016 | 0.0016 | 0.0021 | 0.0014 | 0.0023 |
| L7 | 0.2575 | 0.5341 | 2776 | 0.0007 | 0.0004 | 0.0009 | 0.0009 | 0.0011 | 0.0012 | 0.0014 | 0.0023 | 0.0027 |
| L8 | 0.2588 | 0.5348 | 2746 | 0.0005 | 0.0006 | 0.0005 | 0.0012 | 0.0010 | 0.0012 | 0.0020 | 0.0020 | 0.0018 |
| L9 | 0.2605 | 0.5356 | 2708 | 0.0006 | 0.0007 | 0.0008 | 0.0007 | 0.0013 | 0.0014 | 0.0020 | 0.0019 | 0.0023 |
| L10 | 0.2590 | 0.5338 | 2746 | 0.0002 | 0.0004 | 0.0008 | 0.0006 | 0.0010 | 0.0018 | 0.0013 | 0.0022 | 0.0027 |
| L11 | 0.2584 | 0.5336 | 2759 | 0.0003 | 0.0003 | 0.0005 | 0.0007 | 0.0012 | 0.0011 | 0.0015 | 0.0018 | 0.0019 |
| L12 | 0.2571 | 0.5326 | 2791 | 0.0004 | 0.0008 | 0.0005 | 0.0010 | 0.0014 | 0.0011 | 0.0015 | 0.0019 | 0.0020 |
| L13 | 0.2576 | 0.5341 | 2773 | 0.0004 | 0.0003 | 0.0008 | 0.0009 | 0.0013 | 0.0015 | 0.0015 | 0.0017 | 0.0019 |
| L14 | 0.2619 | 0.5357 | 2680 | 0.0004 | 0.0005 | 0.0008 | 0.0011 | 0.0010 | 0.0014 | 0.0017 | 0.0015 | 0.0018 |
| L15 | 0.2599 | 0.5353 | 2722 | 0.0004 | 0.0007 | 0.0008 | 0.0010 | 0.0011 | 0.0016 | 0.0019 | 0.0016 | 0.0021 |
| L16 | 0.2609 | 0.5351 | 2702 | 0.0003 | 0.0004 | 0.0009 | 0.0010 | 0.0016 | 0.0016 | 0.0020 | 0.0020 | 0.0023 |
| L17 | 0.2586 | 0.5337 | 2754 | 0.0004 | 0.0005 | 0.0006 | 0.0010 | 0.0013 | 0.0012 | 0.0016 | 0.0021 | 0.0024 |
| L18 | 0.2607 | 0.5345 | 2709 | 0.0006 | 0.0005 | 0.0009 | 0.0011 | 0.0010 | 0.0012 | 0.0019 | 0.0023 | 0.0027 |
| L19 | 0.2577 | 0.5342 | 2771 | 0.0006 | 0.0007 | 0.0008 | 0.0011 | 0.0012 | 0.0013 | 0.0020 | 0.0020 | 0.0018 |
| L20 | 0.2620 | 0.5358 | 2677 | 0.0003 | 0.0005 | 0.0008 | 0.0007 | 0.0012 | 0.0017 | 0.0015 | 0.0021 | 0.0026 |
| L21 | 0.2588 | 0.5348 | 2745 | 0.0003 | 0.0003 | 0.0010 | 0.0009 | 0.0012 | 0.0011 | 0.0014 | 0.0018 | 0.0022 |
| L22 | 0.2598 | 0.5346 | 2726 | 0.0007 | 0.0004 | 0.0008 | 0.0007 | 0.0009 | 0.0013 | 0.0016 | 0.0015 | 0.0030 |
| L23 | 0.2567 | 0.5333 | 2795 | 0.0006 | 0.0004 | 0.0008 | 0.0007 | 0.0014 | 0.0018 | 0.0015 | 0.0017 | 0.0024 |
| L24 | 0.2575 | 0.5340 | 2777 | 0.0007 | 0.0005 | 0.0010 | 0.0011 | 0.0011 | 0.0013 | 0.0014 | 0.0016 | 0.0024 |
| L25 | 0.2606 | 0.5357 | 2706 | 0.0004 | 0.0005 | 0.0005 | 0.0010 | 0.0014 | 0.0012 | 0.0016 | 0.0017 | 0.0021 |
| AV | 0.2594 | 0.5346 | 2736 | 0.0004 | 0.0005 | 0.0007 | 0.0009 | 0.0012 | 0.0014 | 0.0017 | 0.0019 | 0.0022 |
| Median | 0.2594 | 0.5347 | 2733 | 0.0004 | 0.0005 | 0.0008 | 0.0010 | 0.0012 | 0.0013 | 0.0016 | 0.0019 | 0.0022 |
| MIN | 0.2567 | 0.5326 | 2653 | 0.0002 | 0.0003 | 0.0004 | 0.0006 | 0.0009 | 0.0011 | 0.0012 | 0.0014 | 0.0017 |
| MAX | 0.2631 | 0.5366 | 2795 | 0.0007 | 0.0008 | 0.0010 | 0.0012 | 0.0016 | 0.0018 | 0.0021 | 0.0023 | 0.0030 |
| STDEV | 0.0017 | 0.0009 | 38.38 | 0.0001 | 0.0002 | 0.0002 | 0.0002 | 0.0002 | 0.0002 | 0.0003 | 0.0003 | 0.0003 |
| N | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 |

4.3 Data Set 2: 85°C, 60 mA (Lumen Maintenance)

| Description of Light Sources Tested: | RF-27TC13DS-EC-N-Y |
|--------------------------------------|--------------------|
| Case Temperature: | 84.7 C |
| Ambient Temperature: | 84.3 C |
| Drive Current: | 60 mA |
| Measure Current: | 60 mA |
| Failures Observed: | None |

Lumen Maintenance (%)

| Sample No. | VF(V) | (lm) | 1000hrs | 2000hrs | 3000hrs | | 5000hrs | 6000hrs | 7000hrs | 8000hrs | 9000hrs |
|------------|-------|-------|---------|---------|---------|--------|---------|---------|---------|---------|---------|
| L26 | 3.06 | 17.1 | 100.16% | 99.86% | 99.48% | 99.17% | 98.76% | 98.30% | 98.04% | 97.40% | 96.96% |
| L27 | 3.06 | 17.2 | 100.19% | 99.87% | 99.59% | 99.09% | 98.74% | 98.25% | 98.04% | 97.34% | 96.99% |
| L28 | 3.06 | 16.7 | 100.15% | 99.88% | 99.58% | 99.08% | 98.76% | 98.28% | 98.03% | 97.35% | 97.00% |
| L29 | 3.06 | 16.8 | 100.08% | 99.89% | 99.51% | 99.19% | 98.82% | 98.35% | 98.02% | 97.42% | 97.00% |
| L30 | 3.06 | 16.8 | 100.12% | 99.87% | 99.53% | 99.14% | 98.68% | 98.38% | 97.84% | 97.31% | 96.98% |
| L31 | 3.04 | 16.7 | 100.18% | 99.93% | 99.46% | 99.21% | 98.80% | 98.41% | 97.85% | 97.32% | 97.02% |
| L32 | 3.04 | 16.7 | 100.13% | 99.97% | 99.58% | 99.17% | 98.80% | 98.37% | 97.90% | 97.34% | 96.90% |
| L33 | 3.04 | 16.7 | 100.12% | 99.87% | 99.54% | 99.13% | 98.82% | 98.35% | 97.83% | 97.34% | 96.99% |
| L34 | 3.04 | 16.7 | 100.08% | 99.88% | 99.54% | 99.09% | 98.69% | 98.27% | 98.00% | 97.36% | 96.99% |
| L35 | 3.04 | 16.8 | 100.18% | 99.92% | 99.46% | 99.13% | 98.79% | 98.33% | 98.00% | 97.40% | 97.08% |
| L36 | 3.04 | 16.8 | 100.11% | 99.86% | 99.43% | 99.09% | 98.69% | 98.22% | 97.90% | 97.40% | 96.92% |
| L37 | 3.04 | 16.8 | 100.19% | 99.86% | 99.52% | 99.10% | 98.75% | 98.27% | 98.04% | 97.39% | 96.97% |
| L38 | 3.04 | 16.8 | 100.18% | 99.87% | 99.59% | 99.09% | 98.74% | 98.26% | 98.03% | 97.34% | 96.99% |
| L39 | 3.04 | 16.3 | 100.08% | 99.88% | 99.53% | 99.18% | 98.80% | 98.34% | 98.02% | 97.39% | 97.00% |
| L40 | 3.04 | 16.3 | 100.09% | 99.88% | 99.53% | 99.19% | 98.70% | 98.37% | 97.94% | 97.34% | 97.00% |
| L41 | 3.04 | 16.3 | 100.17% | 99.89% | 99.48% | 99.18% | 98.69% | 98.40% | 97.85% | 97.31% | 97.00% |
| L42 | 3.04 | 16.3 | 100.14% | 99.97% | 99.54% | 99.20% | 98.80% | 98.38% | 97.88% | 97.33% | 96.91% |
| L43 | 3.04 | 16.3 | 100.13% | 99.89% | 99.56% | 99.15% | 98.81% | 98.36% | 97.88% | 97.34% | 96.96% |
| L44 | 3.07 | 17.0 | 100.09% | 99.87% | 99.54% | 99.11% | 98.75% | 98.32% | 97.95% | 97.36% | 96.99% |
| L45 | 3.07 | 17.0 | 100.08% | 99.89% | 99.53% | 99.11% | 98.73% | 98.32% | 98.00% | 97.38% | 97.02% |
| L46 | 3.08 | 17.0 | 100.11% | 99.89% | 99.46% | 99.09% | 98.72% | 98.31% | 98.06% | 97.40% | 96.94% |
| L47 | 3.08 | 16.4 | 100.14% | 99.88% | 99.48% | 99.17% | 98.76% | 98.26% | 97.90% | 97.40% | 97.06% |
| L48 | 3.07 | 16.4 | 100.16% | 99.89% | 99.61% | 99.12% | 98.84% | 98.24% | 97.97% | 97.34% | 96.86% |
| L49 | 3.07 | 16.4 | 100.19% | 99.90% | 99.48% | 99.19% | 98.65% | 98.41% | 97.82% | 97.38% | 96.94% |
| L50 | 3.05 | 17.0 | 100.08% | 99.91% | 99.63% | 99.15% | 98.79% | 98.37% | 98.01% | 97.34% | 97.05% |
| AV | 3.05 | 16.69 | 100.13% | 99.89% | 99.53% | 99.14% | 98.75% | 98.33% | 97.95% | 97.36% | 96.98% |
| Median | 3.04 | 16.74 | 100.13% | 99.88% | 99.53% | 99.14% | 98.76% | 98.33% | 97.97% | 97.35% | 96.99% |
| MIN | 3.04 | 16.27 | 100.08% | 99.86% | 99.43% | 99.08% | 98.65% | 98.22% | 97.82% | 97.31% | 96.86% |
| MAX | 3.08 | 17.15 | 100.19% | 99.97% | 99.63% | 99.21% | 98.84% | 98.41% | 98.06% | 97.42% | 97.08% |
| STDEV | 0.01 | 0.29 | 0.0004 | 0.0003 | 0.0005 | 0.0004 | 0.0005 | 0.0006 | 0.0008 | 0.0003 | 0.0005 |
| N | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 |

Page 13 of 16

Report No.: 68260LC10007901

4.4 Data Set 2: 85°C, 60 mA (Chromaticity Shift)

| Description of Light Sources Tested: | RF-27TC13DS-EC-N-Y |
|--------------------------------------|--------------------|
| Case Temperature: | 84.7 C |
| Ambient Temperature: | 84.3 C |
| Drive Current: | 60 mA |
| Measure Current: | 60 mA |
| Failures Observed: | None |

Chromaticity Shift (u'v')

| Sample No. | u | V | CCT(K) | 1000 hrs | 2000 hrs | 3000 hrs | 4000 hrs | 5000 hrs | 6000 hrs | 7000 hrs | 8000 hrs | 9000 hrs |
|---------------|--------|--------|--------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| L26 | 0.2609 | 0.5351 | 2702 | 0.0006 | 0.0005 | 0.0005 | 0.0010 | 0.0019 | 0.0022 | 0.0018 | 0.0019 | 0.0034 |
| L27 | 0.2607 | 0.5350 | 2706 | 0.0002 | 0.0009 | 0.0010 | 0.0009 | 0.0012 | 0.0022 | 0.0022 | 0.0027 | 0.0030 |
| L28 | 0.2599 | 0.5354 | 2720 | 0.0002 | 0.0009 | 0.0007 | 0.0014 | 0.0019 | | | | |

0 .35009

4.5 Data Set 3: 105°C, 60 mA (Lumen Maintenance)

| Description of Light Sources Tested: | RF-27TC13DS-EC-N-Y |
|--------------------------------------|--------------------|
| Case Temperature: | 104.8 C |
| Ambient Temperature: | 103.7 C |
| Drive Current: | 60 mA |
| Measure Current: | 60 mA |
| Failures Observed: | None |

Lumen Maintenance (%)

| Sample No | VEVV | (lm) | 1000bro | 2000hra | 2000bro | 4000bro | 5000hra | 6000hra | 7000hra | 9000hra | 0000hra |
|------------|------|-------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
| Sample No. | ` ' | (lm) | 1000hrs | 2000hrs | 3000hrs | 4000hrs | | | 7000hrs | 8000hrs | |
| L51 | 3.05 | 16.9 | 99.62% | 99.42% | 99.02% | 98.67% | 98.14% | 97.72% | 97.52% | 96.87% | 96.51% |
| L52 | 3.05 | 17.0 | 99.70% | 99.44% | 99.06% | 98.60% | 98.16% | 97.90% | 97.46% | 96.83% | 96.49% |
| L53 | 3.07 | 16.8 | 99.66% | 99.43% | 99.07% | 98.70% | 98.20% | 97.83% | 97.42% | 96.82% | 96.47% |
| L54 | 3.07 | 16.8 | 99.70% | 99.41% | 99.02% | 98.62% | 98.34% | 97.92% | 97.38% | 96.87% | 96.43% |
| L55 | 3.07 | 16.8 | 99.60% | 99.43% | 98.96% | 98.66% | 98.32% | 97.87% | 97.52% | 96.86% | 96.40% |
| L56 | 3.11 | 14.9 | 99.59% | 99.44% | 98.95% | 98.65% | 98.21% | 97.72% | 97.49% | 96.92% | 96.45% |
| L57 | 3.10 | 14.9 | 99.68% | 99.44% | 99.09% | 98.71% | 98.34% | 97.77% | 97.41% | 96.85% | 96.44% |
| L58 | 3.10 | 14.9 | 99.59% | 99.38% | 99.03% | 98.70% | 98.24% | 97.82% | 97.48% | 96.81% | 96.47% |
| L59 | 3.06 | 16.6 | 99.63% | 99.37% | 99.07% | 98.67% | 98.14% | 97.90% | 97.27% | 96.84% | 96.54% |
| L60 | 3.06 | 16.6 | 99.62% | 99.37% | 99.02% | 98.58% | 98.14% | 97.71% | 97.44% | 96.87% | 96.49% |
| L61 | 3.06 | 16.6 | 99.64% | 99.42% | 99.02% | 98.66% | 98.15% | 97.73% | 97.48% | 96.86% | 96.50% |
| L62 | 3.05 | 16.8 | 99.67% | 99.43% | 99.07% | 98.65% | 98.16% | 97.86% | 97.42% | 96.83% | 96.48% |
| L63 | 3.05 | 16.8 | 99.66% | 99.41% | 99.05% | 98.69% | 98.32% | 97.83% | 97.42% | 96.83% | 96.44% |
| L64 | 3.05 | 16.8 | 99.66% | 99.43% | 98.96% | 98.63% | 98.34% | 97.90% | 97.45% | 96.86% | 96.43% |
| L65 | 3.06 | 16.8 | 99.59% | 99.44% | 98.95% | 98.66% | 98.29% | 97.80% | 97.50% | 96.90% | 96.44% |
| L66 | 3.06 | 16.9 | 99.68% | 99.44% | 99.08% | 98.66% | 98.23% | 97.74% | 97.48% | 96.86% | 96.45% |
| L67 | 3.06 | 16.9 | 99.61% | 99.42% | 99.03% | 98.71% | 98.32% | 97.81% | 97.42% | 96.85% | 96.47% |
| L68 | 3.05 | 16.8 | 99.61% | 99.38% | 99.05% | 98.69% | 98.17% | 97.89% | 97.35% | 96.82% | 96.53% |
| L69 | 3.05 | 16.8 | 99.62% | 99.37% | 99.07% | 98.61% | 98.14% | 97.90% | 97.34% | 96.84% | 96.54% |
| L70 | 3.05 | 16.8 | 99.62% | 99.37% | 99.02% | 98.66% | 98.14% | 97.72% | 97.46% | 96.87% | 96.50% |
| L71 | 3.07 | 16.8 | 99.68% | 99.39% | 99.05% | 98.59% | 98.32% | 97.74% | 97.39% | 96.85% | 96.47% |
| L72 | 3.07 | 16.8 | 99.64% | 99.39% | 99.12% | 98.70% | 98.25% | 97.78% | 97.31% | 96.89% | 96.53% |
| L73 | 3.07 | 16.8 | 99.68% | 99.38% | 98.95% | 98.71% | 98.18% | 97.72% | 97.37% | 96.91% | 96.49% |
| L74 | 3.06 | 16.6 | 99.68% | 99.38% | 98.93% | 98.70% | 98.25% | 97.74% | 97.49% | 96.91% | 96.52% |
| L75 | 3.07 | 16.8 | 99.69% | 99.46% | 98.97% | 98.70% | 98.30% | 97.72% | 97.40% | 96.81% | 96.56% |
| AV | 3.06 | 16.55 | 99.65% | 99.41% | 99.02% | 98.66% | 98.23% | 97.80% | 97.43% | 96.86% | 96.48% |
| Median | 3.06 | 16.76 | 99.64% | 99.42% | 99.03% | 98.66% | 98.23% | 97.80% | 97.42% | 96.86% | 96.48% |
| MIN | 3.05 | 14.86 | 99.59% | 99.37% | 98.93% | 98.58% | 98.14% | 97.71% | 97.27% | 96.81% | 96.40% |
| MAX | 3.11 | 16.95 | 99.70% | 99.46% | 99.12% | 98.71% | 98.34% | 97.92% | 97.52% | 96.92% | 96.56% |
| STDEV | 0.02 | 0.64 | 0.0004 | 0.0003 | 0.0005 | 0.0004 | 0.0008 | 0.0007 | 0.0007 | 0.0003 | 0.0004 |
| N | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 | 25 |
| | | | | | | | | | | | |

Page 15 of 16

Report No.: 68260LC10007901

4.6 Data Set 3: 105°C, 60 mA (Chromaticity Shift)


| Description of Light Sources Tested: | RF-27TC13DS-EC-N-Y |
|--------------------------------------|--------------------|
| Case Temperature: | |
| <u> </u> | |
| Ambient Temperature: | |
| Drive Current: | 60 mA |
| Measure Current: | 60 mA |
| Failures Observed: | None |

Chromaticity Shift (u'v')

| Sample No. | u | V | CCT(K) | 1000 hrs | 2000 hrs | 3000 hrs | 4000 hrs | 5000 hrs | 6000 hrs | 7000 hrs | 8000 hrs | 9000 hrs |
|---------------|--------|--------|--------|-------------|-----------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| L51 | 0.2629 | 0.5365 | 2658 | 0.0010 | 0.0007 | 0.0015 | 0.0014 | 0.0024 | 0.0029 | 0.0025 | 0.0028 | 0.0035 |
| L52 | 0.2597 | 0.5352 | 2726 | 0.0008 | 0.0011 | 0.0014 | 0.0019 | 0.0022 | 0.0019 | 0.0025 | 0.0030 | 0.0039 |
| L53 | 0.2597 | 0.5352 | 2726 | 0.0009 | 0.0007 | 0.0017 | 0.0010 | 0.0019 | 0.0029 | 0.0025 | 0.0028 | 0.0028 |
| L54 | 0.2590 | 0.5338 | 2747 | 0.0005 | 0.0008 | 0.0015 | 0.0011 | 0.0014 | 0.0020 | 0.0033 | 0.0028 | 0.0034 |
| L55 | 0.2589 | 0.5338 | 2747 | 0.0007 | 0.0009 | 0.0014 | 0.0015 | 0.0014 | 0.0018 | 0.0032 | 0.0025 | 0.0038 |
| L56 | 0.2597 | 0.5346 | 2728 | 0.0003 | 0.0015 | 0.0010 | 0.0018 | 0.0020 | 0.0024 | 0.0028 | 0.0029 | 0.0034 |
| L57 | 0.2597 | 0.5345 | 2729 | 0.0009 | 0. 26 06 | 0.0019 | 0.0017 | 0.0015 | 0.0024 | 0.0033 | 0.0028 | 0.0035 |
| L58 | 0.2576 | 0.5341 | 2773 | 0.0003 | 0.0012 | 0.0011 | 0.0010 | 0.0017 | 0.0018 | 0.0023 | 0.0033 | 0.0033 |
| L59 | 0.2585 | 0.5336 | 2756 | 0.0009 | 0.0010 | 0.0016 | 0.0014 | 0.0018 | 0.0029 | 0.0024 | 0.0033 | 0.0027 |
| L60 | 0.2582 | | | | | | | | | | | |

5 EUT Photo

5.1 EUT PHOTO

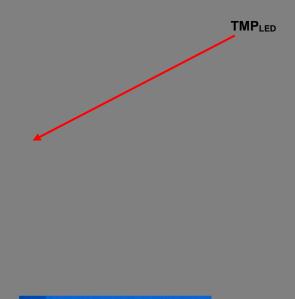

*****END OF TEST REPORT*****